

DuPont LF121

PALLADIUM /SILVER CONDUCTOR

Technical Data Sheet

Product Description

DuPont LF121 palladium/silver conductor composition is intended to be applied to ceramic substrates by screen printing and firing in a conveyor furnace in an air (oxidizing) atmosphere. It has been developed to form interconnecting tracks and pads for component and lead attachment, in hybrid microcircuits and networks.

Product Benefits

- Excellent fine line resolution
- Lead, cadmium, and nickel free*
- Excellent solderability with lead and lead-free solders.
- Excellent green-strength
- Compatible, sequentially or co-fired, with DuPont LF151 dielectric as a crossover

*Cadmium, lead and nickel "free" as used herein means that these are not intentionally added to the referenced product. Trace amounts however may be present.

Processing Conditions

Printing

200 - 325 mesh stainless steel, 0.3 - 0.5 mil emulsion. Print speeds up to 20 cm/s.

Drying

Allow prints to level for 5 - 10 minutes at room temperature, then dry for 10 - 15 minutes at 150°C.

Firing


850°C peak held for 10 minutes on 30 minutes cycle in air (oxidizing) atmosphere.

Composition Properties

Test	Properties
Viscosity (Pa.s) [Brookfield HBT, UC&SP @10 rpm, 25°C]	150 - 250
Thinner	DuPont 4553
Retest (months)	6
Typical Composition Properties	
Shrinkage (dried to fired) [%]	22 - 28
Mean fired thickness: (using 200	12 - 16, typical 14
Coverage @ 16µm fired (cm ² /g)	67 - 72
Resistivity (mΩ/sq @ 16µm)	≤ 30
Soldered Adhesion ¹	
Initial (N)	≥ 18
Aged (48hrs @ 150°C)[N]	≥ 18
<small>¹ 90° wire peel test on 2mm x 2mm pad soldered with 95.5Sn/3.8Ag/0.7Cu Solder using mildly activated flux, Alpha 611 on both Alumina.</small>	

This table shows anticipated typical physical properties for DuPont LF121 based on specific controlled experiments in our labs and are not intended to represent the product specifications, details of which are available upon request.

Figure 1 - 30 Minutes Profile

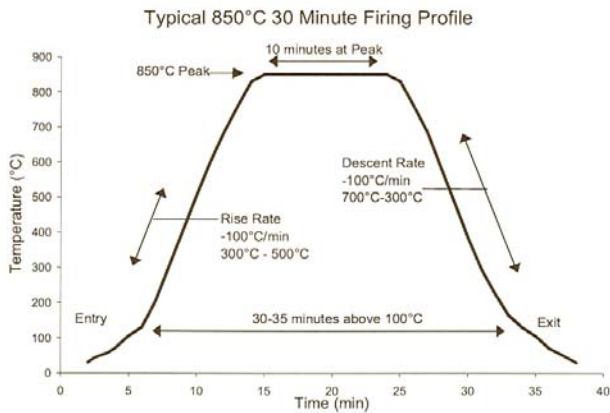

Processing Substrates

Substrates of different compositions and from various manufacturers may result in variation in performance properties. DuPont LF121 is recommended for Al₂O₃ substrates only.

Thinner

This composition is optimized for screen printing, thinning is not normally required. Use the DuPont recommended thinner for slight adjustments to viscosity or to replace evaporation losses. The use of too much thinner or the use of a non recommended thinner may affect the rheological behavior of the material and its printing characteristics.

General

Performance will depend to a large degree on care exercised in screen printing. Care should be taken to keep the composition, printing screens and other tools free of metal contamination. Dust, lint and other particulate matter may also contribute to poor yields.

Storage and Shelf Life

Containers should be stored, tightly sealed, in a clean, stable environment at room temperature (<25°C). Shelf life of material in unopened containers is six months from date of shipment. Some settling of solids may occur and compositions should be thoroughly mixed prior to use.

Safety and Handling

For Safety and Handling information pertaining to this product, read the Material Safety Data Sheet (MSDS).



The miracles of science™

For more information on DuPont LF121 or other DuPont Microcircuit Materials products, please contact your local representative:

Americas

DuPont Microcircuit Materials
14 T.W. Alexander Drive
Research Triangle Park, NC 27709

Tel.: 800-284-3382

Europe

Du Pont (U.K.) Limited
Coldharbour Lane
Bristol BS16 1QD
U.K.

Tel.: 44-117-931-3191

Asia

DuPont Kabushiki Kaisha
MCM Technical Lab
DuPont Electronics Center
KSP R&D B213
2-1, Sakado 3-chom, Takatsu-ku,
Kawasaki-shi, Kanagawa, 213-0012
Japan
Tel +81 44 820 7575

DuPont Taiwan Ltd
45, Hsing-Pont Road,
Taoyuan, Taiwan 330
Tel.: 886-3-377-3616

DuPont China Holding Co. Ltd
Bldg 11, 399 Keyuan Rd., Zhangji Hi-Tech Park,
Pudong New District, Shanghai 201203, China
Tel.: 86-21-6386-6366 ext.2202

DuPont Korea Inc.
3~5th Floor, Asia tower #726,
Yeoksam-dong, Gangnam-gu
Seoul 135-719, Korea
Tel.: 82-10-6385-5399

E. I. DuPont India Private Limited
7th Floor, Tower C, DLF Cyber Greens,
Sector-25A, DLF City, Phase-III,
Gurgaon 122 002 Haryana, India
Tel.: 91-124-4091818

Du Pont Company (Singapore) Pte Ltd
1 HarbourFront Place, #11-01
HarbourFront Tower One,
Singapore 098633
Tel.: 65-6586-3022

<http://mcm.dupont.com>

Copyright © 2009 DuPont. All rights reserved. The DuPont Oval, DuPont™, The miracles of science™, Green Tape™ and all products or words denoted with © or ™ are registered trademarks or trademarks of E. I. du Pont de Nemours and Company or its affiliates (“DuPont”).
NO PART OF THIS MATERIAL MAY BE REPRODUCED, STORED IN A RETRIEVAL SYSTEM OR TRANSMITTED IN ANY FORM OR BY ANY MEANS ELECTRONIC, MECHANICAL, PHOTOCOPYING, RECORDING OR OTHERWISE WITHOUT THE PRIOR WRITTEN PERMISSION OF DUPONT.

Caution: Do not use in medical applications involving implantation in the human body or contact with internal body fluids or tissue unless the product is provided by DuPont under a formal written contract consistent with the DuPont Policy Regarding Medical Applications of DuPont Materials H-50103-2 (“Medical Applications Policy”) and which expressly acknowledges the contemplated use. For additional information, please request a copy of DuPont Medical Caution Statement H-50102-2 and the DuPont Medical Applications Policy.

The information provided herein is offered for the product user’s consideration and examination. While the information is based on data believed to be reliable, DuPont makes no warranties, expressed or implied as to the data’s accuracy or reliability and assumes no liability arising out of its use. The data shown are the result of DuPont laboratory experiments and are intended to illustrate potential product performance within a given experimental design under specific, controlled laboratory conditions. While the data provided herein falls within anticipated normal range of product properties based on such experiments, it should not be used to establish specification limits or used alone as the basis of design. It is the product user’s responsibility to satisfy itself that the product is suitable for the user’s intended use. Because DuPont neither controls nor can anticipate the many different end-uses and end-use and processing conditions under which this information and/or the product described herein may be used, DuPont does not guarantee the usefulness of the information or the suitability of its products in any given application. Users should conduct their own tests to determine the appropriateness of the products for their particular purpose.

The product user must decide what measures are necessary to safely use the product, either alone or in combination with other products, also taking into consideration the conditions of its facilities, processes, operations, and its environmental, health and safety compliance obligations under any applicable laws.

This information may be subject to revision as new knowledge and experience become available. This publication is not to be taken as a license to operate under, or recommendation to infringe any patent.



The miracles of science™

MCMLF121 (10/2014)