

DuPont™ Vespel® CR-6100

Compression molded parts and shapes

FEATURES/BENEFITS

Description

DuPont™ Vespel® CR-6100 is a composite material designed for use in hostile chemical environments. Stationary parts in this composite material meet the following specification per API STD/ISO 13709, Centrifugal Pumps For Petroleum Petrochemical and Natural Gas Industries: -46 to 230 °C (-50 to 450 °F) temperature limits and 2,000 kPa (20 bar; 300 psi) limiting pressure differential per wear part linear measure of 25 mm (1.0 inch).

Due to its low creep and high thermal resistance, Vespel® CR-6100 often excels where other chemically-resistant plastics fall short. This makes Vespel® CR-6100 particularly well suited for seals, wear rings and other components used in a variety of devices and operating conditions.

Typical Properties of DuPont™ Vespel® CR-6100


Mechanical Property	Temperature	Test Method	Direction	SI (English) Units	Typical Values
Compressive Strength	23 °C (73 °F)	ASTM D-695	x-y z	MPa (ksi)	87 (12.6) 174 (25.2)
Compressive Modulus	23 °C (73 °F)	ASTM D-695	x-y z	MPa (ksi)	8,520 (1,240) 2,070 (300)
Compressive Strength	260 °C (500 °F)	ASTM D-695	x-y z	MPa (ksi)	18 (2.6) 84 (12.2)
Compressive Modulus	260 °C (500 °F)	ASTM D-695	x-y z	MPa (ksi)	1,730 (250) 720 (104)
Flexural Strength	23 °C (73 °F)	ASTM D-790	x-y	MPa (ksi)	156 (22.7)
Flexural Modulus	23 °C (73 °F)	ASTM D-790	x-y	MPa (ksi)	9,530 (1,380)
Flexural Strength	260 °C (500 °F)	ASTM D-790	x-y	MPa (ksi)	43 (6.3)
Flexural Modulus	260 °C (500 °F)	ASTM D-790	x-y	MPa (ksi)	3,720 (540)
Tensile Strength	23 °C (73 °F)	ASTM D-3039	x-y z	MPa (ksi)	120 (17.6) 17 (2.5)
Tensile Modulus	23 °C (73 °F)	ASTM D-3039	x-y z	MPa (ksi)	9,790 (1,420) 2,680 (390)
Tensile Elongation	23 °C (73 °F)	ASTM D-3039	x-y z	%	1.3 0.4
Tensile Strength	260 °C (500 °F)	ASTM D-3039	x-y z	MPa (ksi)	52 (7.6) 2.8 (0.4)
Tensile Modulus	260 °C (500 °F)	ASTM D-3039	x-y z	MPa (ksi)	2,800 (405) 330 (47.4)
Tensile Elongation	260 °C (500 °F)	ASTM D-3039	x-y z	%	1.2 1.6
Notched Izod Impact	23 °C (73 °F)	ASTM D-256	x-y z	J/m (ft-lb/inch)	150 (3) 85 (2)
Un-Notched Izod Impact	23 °C (73 °F)	ASTM D-256	x-y z	J/m (ft-lb/inch)	260 (5) 180 (3)

(continued)

Typical Properties of DuPont™ Vespel® CR-6100 (continued)

Thermal Property	Temperature	Test Method	Direction	SI (English) Units	Typical Values
CTE, Linear	23–260 °C (73–500 °F)	ASTM E-831	x-y	10 ⁻⁶ m/m °C (10 ⁻⁶ in/in °F)	5.6 (31)
	35–149 °C (95–300 °F)		z		300 (170)
	149–204 °C (300–399 °F)		z		470 (260)
	204–260 °C (399–500 °F)		z		750 (420)
Heat Deflection Temperature at 264 psi	–	ASTM D-648	x-y z	°C (°F)	315 (600) 120 (250)
Thermal Conductivity	23–149 °C (73–30 °F)	Hot Wire Method	–	W/m-K (BTU-in/hr-ft ² -°F)	0.7 (4.7)
Wear Property	Condition	Test Method	Direction	SI (English) Units	Typical Values
PV Limit	1.72 MPa (250 psi)	Internal Test Falex	x-y	MPa·m/s (psi·ft/min)	9.7 (278,000)
Other Property	Condition	Test Method	Direction	SI (English) Units	Typical Values
Specific Gravity	23 °C (73 °F)	ASTM D-792	–	–	2.06
Hardness	23 °C (73 °F)	ASTM D-2240	x-y	Shore D	82
			z		84
Interlaminar Shear Strength	23 °C (73 °F)	Internal Test	x-y	MPa (ksi)	17 (2.4)
Water Absorption, 24 hr	23 °C (73 °F)	ASTM D-570	–	% by weight	0.01

NOMENCLATURE

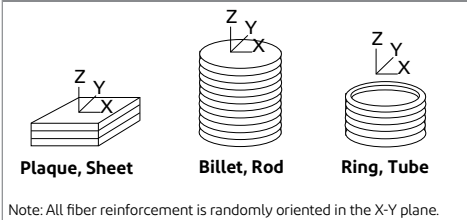

Visit us at vespel.com

The information set forth herein is furnished free of charge, is based on technical data that DuPont believes to be reliable and represents typical values that fall within the normal range of properties. This information relates only to the specific material designated and may not be valid for such material used in combination with other materials or in other processes. It is intended for use by persons having technical skill, at their own discretion and risk. This information should not be used to establish specification limits nor used alone as the basis of design. Handling precaution information is given with the understanding that those using it will satisfy themselves that their conditions of use present no health or safety hazards and comply with applicable law. Since conditions of product use and disposal are outside our control, we make no warranties, express or implied, and assume no liability in connection with any use of this information. As with any product, evaluation under end use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate or a recommendation to infringe on patents.

CAUTION: Do not use DuPont materials in medical applications involving implantation in the human body or contact with internal body fluids or tissues unless the material has been provided from DuPont under a written contract that is consistent with the DuPont policy regarding medical applications and expressly acknowledges the contemplated use. For further information, please contact your DuPont representative.

DuPont's sole warranty is that our products will meet our standard sales specifications in effect at the time of shipment. Your exclusive remedy for breach of such warranty is limited to refund of purchase price or replacement of any product shown to be other than as warranted. TO THE FULLEST EXTENT PERMITTED BY APPLICABLE LAW, DUPONT SPECIFICALLY DISCLAIMS ANY OTHER EXPRESS OR IMPLIED WARRANTY OF FITNESS FOR A PARTICULAR PURPOSE, MERCHANTABILITY, OR NON-INFRINGEMENT. DUPONT DISCLAIMS LIABILITY FOR ANY SPECIAL, INCIDENTAL, OR CONSEQUENTIAL DAMAGES.

DuPont™, the DuPont Oval Logo, and all trademarks and service marks denoted with ™, SM or ® are owned by affiliates of DuPont de Nemours, Inc. unless otherwise noted. © 2022 DuPont. All rights reserved.

Reference No. VPE-A-10840-00-A0111 0422 CDP



dupont.com